


Historic, archived document

Do not assume content reflects current scientific knowledge, policies, or practices.



UNITED STATES DEPARTMENT OF AGRICULTURE

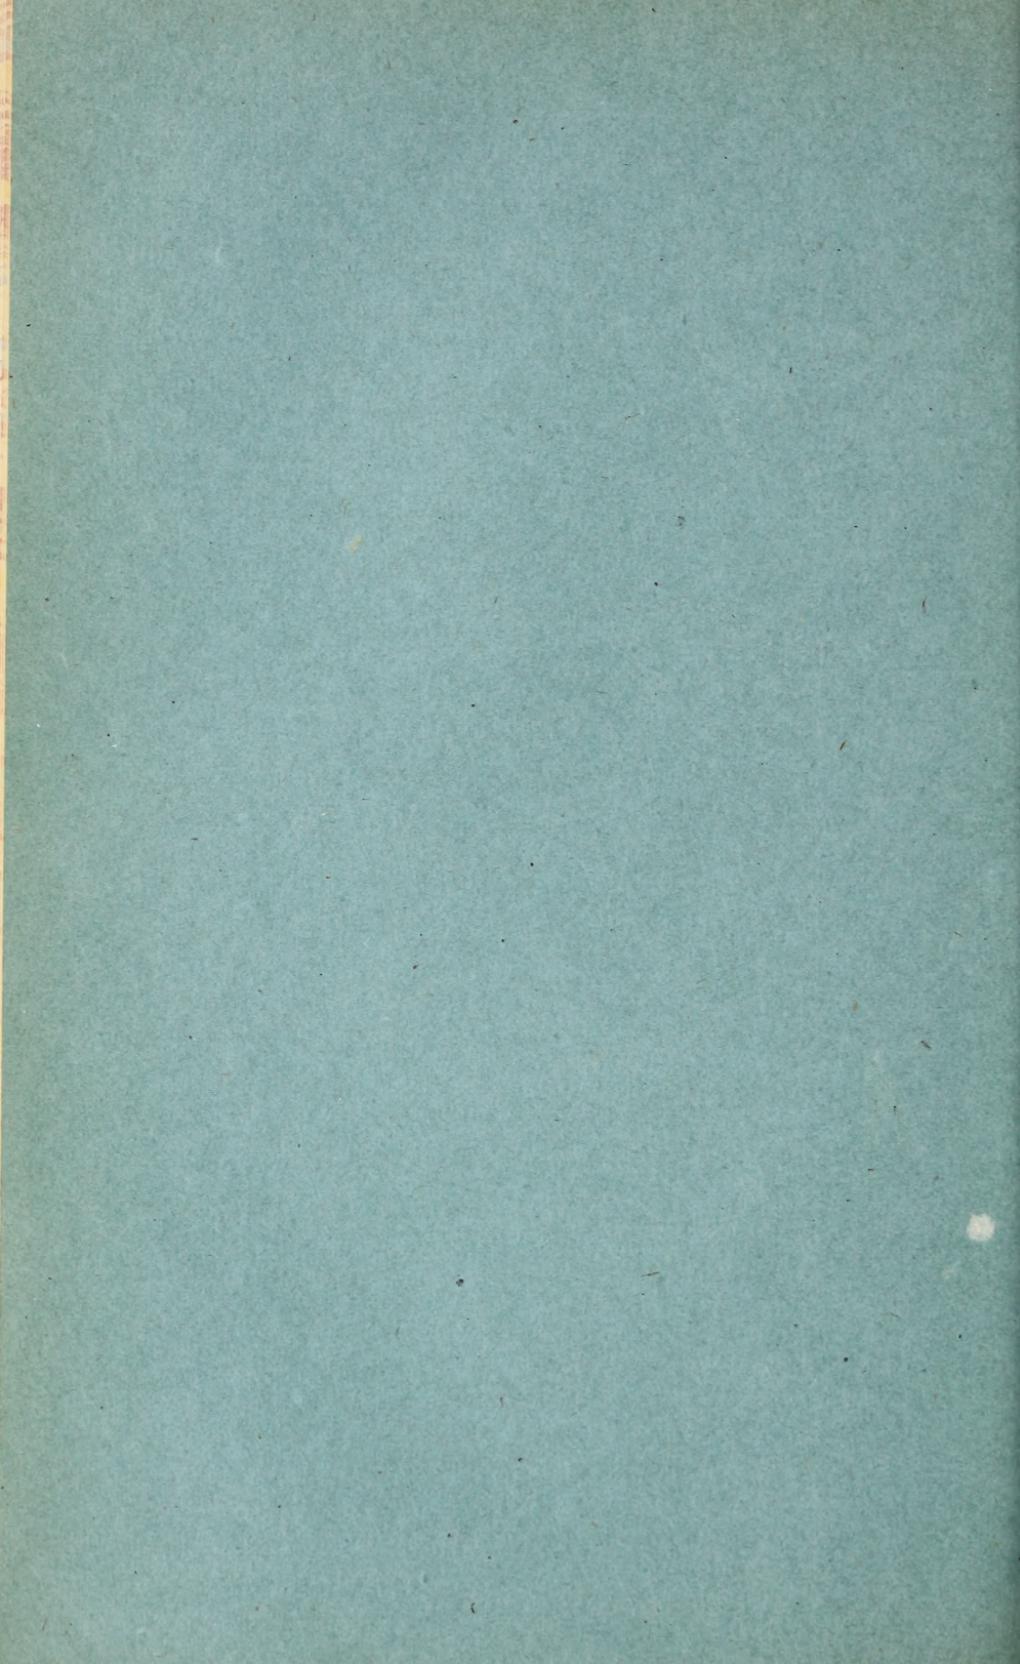

BULLETIN No. 537

Contribution from Office of Public Roads and Rural Engineering.
LOGAN WALLER PAGE, Director.

Washington, D. C.

PROFESSIONAL PAPER

April 21, 1917

THE RESULTS OF PHYSICAL TESTS OF ROAD-BUILDING ROCK IN 1916, INCLUDING ALL COMPRESSION TESTS.

By PRÉVOST HUBBARD, *Chemical Engineer*, and FRANK H. JACKSON, JR., *Assistant Testing Engineer*.

CONTENTS.

	Page.	Page.	
Introduction.....	1	Table III.—Geographical distribution of rock samples tested to January 1, 1917.....	22
Crushing strength or compression test.....	1	Table IV.—General limiting test values for broken stone.....	23
Interpretation of results of physical tests.....	2		
Table I.—Results of physical tests of road-building rock in 1916.....	3		
Table II.—Results of compression tests of rock to January 1, 1917.....	17		

INTRODUCTION.

This bulletin should be considered as a supplement to United States Department of Agriculture Bulletin 370, which gives the results of the more common physical tests of some 3,650 road-building rock examined by the Office of Public Roads and Rural Engineering to January 1, 1916. The office tested 396 samples of rock in 1916, the results of which tests are given in Table I, the rocks being classified according to their location. It should be noted that in a number of cases, in addition to other tests, the crushing strength of the rock also is given. This test is not made ordinarily when examining rock to determine its suitability for use in various types of broken-stone roads. The test is employed often, however, when considering a rock for use in the manufacture of paving block, and as many requests for records of the crushing strength of various rocks have been received in the past year, it has been thought advisable to give in Table II a complete record of all of the crushing-strength tests made by the office up to January 1, 1917. Following is a brief description of this test, as made by the office.

CRUSHING STRENGTH OR COMPRESSION TEST.

The compression test is made upon a cylindrical test specimen 2 inches in diameter and 2 inches high. Both ends of the specimen, which have been sawed at right angles to the axis of the cylinder,

and properly faced, are bedded in plaster of Paris. The cylinder then is crushed in a 200,000-pound universal testing machine. A small 2-inch spherical bearing block is placed between the moving head of the machine and the upper surface of the specimen. The average of at least two determinations is reported as the crushing strength, calculated in pounds per square inch. Crushing strength tests are made upon samples of road-building rock only when especially requested. Of a total of 282 compression tests made up to January 1, 1917, Table II shows that 97 were made on granites, 13 on gneisses, 78 on limestones, 42 on dolomites, 28 on sandstones, and 24 on various other types of material.

The percentage variation in the strength of the 110 granites and gneisses and the 120 limestones and dolomites is shown graphically in figure 1. In this chart the per cent of total samples tested having various values for crushing strength are plotted as indicated. For instance, the chart shows that 10 per cent of all granites and gneisses tested show a crushing strength of 20,000 pounds per square inch. Likewise, by summing up all the per cents to the left of the 20,000-pound

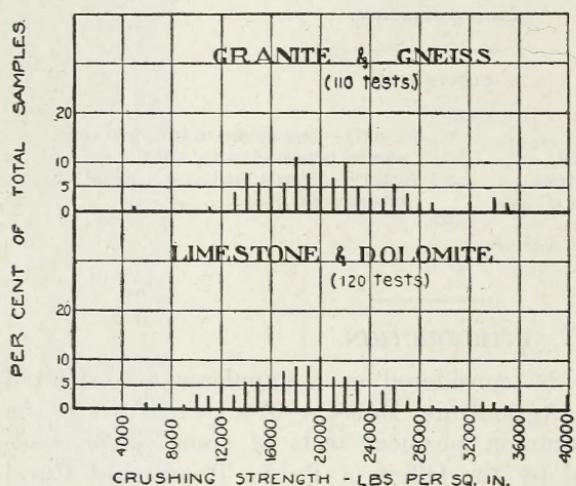


FIG. 1.—Variations in the crushing strength of rock.

line we find that 48 per cent of all samples of granite and gneiss tested have a crushing strength of less than 20,000 pounds per square inch, which shows that the average crushing strength of this type of material lies between 19,000 and 20,000 pounds per square inch. Likewise, the average crushing strength of the limestones and dolomites lies between 18,000 and 19,000 pounds per square inch.

INTERPRETATION OF RESULTS OF PHYSICAL TESTS.

A discussion of the interpretation of the results of physical tests was given in Bulletin 370, to which reference has been made. Since the publication of that bulletin, however, a table of general limiting test values for broken stone for various types of road construction has been adopted by the office and printed on the back of its form for reporting tests. For general reference these limiting values, together with comments upon limits shown, are given in Table IV.

TABLE I.—*Results of physical tests of road-building rock from the United States, Canada, Porto Rico, and Cuba, from Jan. 1, 1916, to Jan. 1, 1917.*

ALABAMA.

Serial No.	Town or city.	County.	Name of material.	Crushing strength, pounds per square inch.	Weight per cubic foot.	Absorption per cubic foot.	Per cent coefficient of wear.	French coefficient of wear.	Hardness.	Toughness.	Cementing value.
10138	Bridgeport.	Jackson.	Oolitic limestone.	(1)	Pounds. 108 168	Pounds. .21 .55	(1) 6.5 2.3	(1) 6.2 17.4	18.7 15.3 19.0	13 6 32	17 25 (1)
9985	Birmingham.	Jefferson.	Limestone.	(1)					15.7 5	41 40	

ARKANSAS.

9828	Lamar.	Johnson.	Feldspathic sandstone.....	21,980	159	1.98	(1) 6.5 .42	(1) 6.2 2.3	18.7 15.3 19.0	13 6 32	17 25 (1)
9838	Fort Smith.	Sebastian.	Sandstone.....	(1)	150	5.00					
10486	Gillham.	Searcy.	Feldspathic quartzite.....	(1)	164	.42					

COLORADO.

9821	Lyons (near).	Boulder.	Argillaceous limestone.....	(1)	162	2.98	4.9	8.2	15.3	7	162
9822	Lyons.	do.	Sandstone.....	(1)	156	1.73	3.4	11.8	18.3	11	36
9823	Lyons (near).	do.	do.....	(1)	156	1.37	2.9	13.8	16.0	14	13
11168	Denver.	Jefferson.	Augite andesite.....	(1)	169	1.27	2.7	14.8	15.3	17	98
11169	do.	Denver.	Smelter slag.....	(1)	216	.65	7.6	(1)	(1)	6	6
11170	do.	do.	do.....	(1)	217	.30	5.1	7.8	(1)	15	4
11171	do.	do.	do.....	(1)	217	.86	4.6	8.7	17.3	15	

CONNECTICUT.

9944	Plainville.	Hartford.	Diabase.....	(1)	184	1.14	2.0	20.0	19.0	23	102
11151	Bast Haven.	New Haven.	Altered basalt.....	(1)	169	.63	3.7	10.8	17.3	10	72
11067	Waterford.	New London.	Granite.....	(1)	162	1.74	(1)	(1)	18.7	13	(1)
11068	do.	do.	Biotite granite.....	(1)	162	.78	(1)	(1)	18.7	8	(1)
11069	do.	do.	do.....	(1)	164	.71	(1)	(1)	18.7	14	(1)
9791	Oneida.	Windham.	do.....	(1)	164	(1)	(1)	(1)	18.3	8	(1)
11098	do.	do.	do.....	(1)	163	.55	(1)	(1)	18.7	6	(1)
11099	do.	do.	Gneissoid granite.....	(1)	163	.67	(1)	(1)	18.7	6	(1)
11148	(2).	do.	do.....	(1)	163	.44	4.6	8.7	18.7	7	(1)

¹ Test not made.² Exact locality not known.

TABLE I.—Results of physical tests of road-building rock from the United States, Canada, Porto Rico, and Cuba, from Jan. 1, 1916, to Jan. 1, 1917—Con.
FLORIDA.

Serial No.	Town or city.	County.	Name of material.	Crushing strength, pounds per square inch.	Weight per cubic foot.	Absorption per cubic foot.	Per cent of wear.	French coefficient of wear.	Hardness.	Toughness.	Cementing value.
10776	(2) Delray (3 miles west)	Broward	Siliceous limestone	(1)	Pounds.	Pounds.	(1)	(1)	17.3	6	61
10411	Boynton (near) ...	Palm Beach	Shell limestone	(1)	(1)	(1)	50.9	0.8	(1)	12	52
10430	Jupiter (15 miles west)	do	do	(1)	(1)	(1)	37.2	1.1	(1)	7	40
10431	Jupiter (15 miles west)	do	do	(1)	(1)	(1)	12.5	3.2	14.7	5	43
GEORGIA											
10398	Cartersville (3 miles east)	Bartow	Quartz schist	159	0.71	5.0	19.3	8.0	(1)	11	(1)
10399	Cartersville	do	Feruginous sandstone	145	8.74	22.0	1.8	(1)	12	(1)	42
10400	Cass Station (2 miles north)	do	Sandstone	152	2.86	(1)	14.9	18.7	12	7	7
10192	Titusville	Brevard	Shell limestone	155	4.03	7.5	5.3	14.9	17.7	17.7	5
10345	Carrollton (4 miles north)	Carroll	Biotite gneiss	172	.33	4.7	8.5	18.7	18.7	18.7	5
10646	Carrollton (2 miles southwest)	do	Granite gneiss	165	.62	4.5	8.9	18.5	18.5	18.5	6
10647	Carrollton (2 miles southwest)	do	do	169	.51	4.6	8.7	18.5	18.5	18.5	6
10648	Carrollton (7 miles northeast)	do	Biotite gneiss	168	.53	4.8	8.3	18.7	18.7	18.7	4
10654	Temple (4 miles east)	do	Biotite gneiss	166	.67	(1)	18.0	10.5	10.5	10.5	4
10649	Carrollton (4 miles southeast)	do	Biotite schist	169	.56	7.7	5.2	17.0	17.0	17.0	5
10651	Mabryville	do	Epidote hornblende schist	168	.51	5.7	7.0	18.9	18.9	18.9	8
10633	Roopville	do	Mica schist	192	1.12	5.5	7.3	17.7	17.7	17.7	9
10637	Bowdon (1 mile north)	do	Amphibolite	168	.75	(1)	16.7	16.7	16.7	16.7	27
10417	Athens	Clarke	Biotite granite	187	1.20	19.0	2.1	10.5	10.5	10.5	4
10422	Athens (4 miles west)	do	do	165	1.68	6.4	6.3	18.7	18.7	18.7	6
10423	Athens (4 miles from)	do	do	163	1.56	(1)	15.4	4.4	4.4	4.4	4
10420	Athens	do	do	163	.58	4.4	9.1	17.8	17.8	17.8	9
10418	do	do	do	167	1.47	5.9	6.8	18.7	18.7	18.7	6
10421	Athens (south of)	do	Granite gneiss	169	.76	7.5	5.3	17.7	17.7	17.7	6
10378	Marietta (1/2 miles south)	Cobb	Biotite gneiss	167	.65	(1)	18.7	18.7	18.7	18.7	6
10380	Chattahoochee River	do	do	170	1.67	6.5	6.2	17.3	17.3	17.3	6
10381	Lost Mountain Store	do	Hornblende gneiss	165	.26	5.1	7.8	18.6	18.6	18.6	8
10382	Southeast Kennesaw Mountain	do	Felspathic gneiss	188	.93	(1)	13.3	13.3	13.3	13.3	4
10387	Marietta (4 miles northwest)	do	Biotite gneiss	167	.73	(1)	18.7	18.7	18.7	18.7	6
10388	Acworth (2 miles south)	do	do	169	.50	5.6	7.1	17.3	17.3	17.3	6
10389	Acworth (4 miles south)	do	do	175	.68	8.6	4.7	16.7	16.7	16.7	5
10389	Austell (1 mile west)	do	do	174	.59	10.1	3.9	16.7	16.7	16.7	5
			Granite gneiss	(1)							18.7

TESTS OF ROAD-BUILDING ROCK IN 1916.

5

10293	Blackwell Station (1 mile north)	do	Hornblende gneiss	17.3	7	(1)
10294	Kennear Mountain (north of)	do	Magnetic quartzite	18.0	7	(1)
10279	Smyrna (3½ miles west)	do	Amphibolite	18.0	7	(1)
10395	Kennear Station (4 miles southwest).	do	Siliceous shell limestone	15.3	5	(1)
9869	Lela.	Deeatur.	Calcareous shale	4.9	20	(1)
10197	Beach Creek Bridge.	Floyd.	Sandstone	.42	20	(1)
10199	Beacher Mountain.	do	Limestone	1.05	7	(1)
10198	Hufaker Station.	do	Argillaceous limestone	.84	7	(1)
10200	Rome (3 miles north).	do	Limestone	.46	7	(1)
10202	Dozier Creek.	do	do	5.3	5	(1)
10203	Pinson.	do	Argillaceous limestone	125	2.51	(1)
10211	Rome.	do	Crystalline limestone	163	2.14	(1)
10221	Armuchee (1 mile southeast).	do	Oolitic limestone	163	1.47	(1)
10222	do	do	Limestone	170	.22	3.6
10223	do	do	do	168	.21	5.1
10224	Armuchee (southeast of).	do	Argillaceous limestone	170	.44	5.1
9751	Atlanta (near).	Fulton.	Biotite granite	169	.22	7.8
9761	do	do	Gneissoid granite	167	4.9	19.3
9761	Atlanta.	do	do	162	.85	8.2
9753	Atlanta (near).	do	do	168	.35	5.6
9752	do	do	do	165	.53	7.3
9754	do	do	do	165	.94	4.2
9755	Atlanta.	do	do	165	.38	9.5
9756	Atlanta (near).	do	Mica gneiss.	165	.30	10.5
9757	do	do	do	165	4.3	16.7
9758	Atlanta.	do	do	165	1.01	4.0
9759	Atlanta (near).	do	do	165	4.1	8.5
9760	Atlanta (near).	do	do	168	.30	10.5
9762	do	do	do	165	.40	3.8
9763	do	do	Biotite gneiss	172	1.03	11.4
9763	Atlanta.	do	Hornblende gneiss	184	.08	18.4
9766	do	do	Biotite gneiss	165	.18	13.3
9767	do	do	do	165	.36	18.7
10396	Fairmount (½ mile south).	Gordon.	Granite gneiss.	175	.26	9.1
10397	do	do	Limestone	169	.27	7.5
10547	Lawrenceville.	Gwinnett.	do	170	.08	4.1
10556	Lawrenceville (12 miles north-east).	do	Biotite hornblende schist	183	.60	15.7
10553	Lawrenceville.	do	Hornblende schist	196	.65	6.1
10564	Rose Hill.	do	Granite gneiss	159	.62	17.0
10565	Shelville.	do	Biotite gneiss	162	.73	18.9
10554	Lawrenceville.	do	do	165	.55	5.6
10555	Lawrenceville (½ miles east).	do	Granite.	162	.33	7.3
10557	Lawrenceville (6 miles south-east).	do	do	162	.86	19.2
10558	do	do	do	162	.72	14.7
10559	Grayson (2 miles east).	do	Biotite granite	162	.61	4.6
10560	McElvaneey Shoals.	do	Gneissoid granite	158	.71	8.7
10561	Grayson (southwest of).	do	do	162	.71	5.2
10562	Langley Quarry.	do	Granite.	162	.67	7.7
				162	.82	6.0

² Exact locality not known.¹ Test not made.

TABLE I.—*Results of physical tests of road building rock from the United States, Canada, Porto Rico, and Cuba, from Jan. 1, 1916, to Jan. 1, 1917*—Con.

GEORGIA—Continued.

IDAHO.

10462 St. Anthony Fremont Bassit (1) 159 4.17 7.2 5.6 16.7 4 (1)

TESTS OF ROAD-BUILDING ROCK IN 1916.

ILLINOIS.

9750	Aurora.....		
10367	Kankakee.....		
10298	Fox Township.....		
11133	Pontiac.....		
9837	Joliet.....		
10772	Aurora.....		
	do.....		

ILLINOIS.

9688	Kane.....		
11082	Brazial.....		
11018	Milltown.....		
11019	do.....		
11020	do.....		
11021	do.....		
11022	do.....		
11023	do.....		
11024	do.....		
11025	do.....		
9859	St. Paul.....		
10114	do.....		
11066	Schenkville.....		
11182	Huntington.....		
9811	Vernon.....		
10834	do.....		
10847	do.....		
10256	Bloomington (east of).....		
10257	Bloomington.....		
10493	do.....		
9860	Greencastle.....		
10519	Filmore.....		
10520	do.....		
10727	Greencastle.....		
10020	Elbertfield.....		
9935	Bluffton.....		
10633	(2).....		
(2)	(2).....		
10694	(2).....		

INDIANA.

9688	Clark.....		
11082	Clay.....		
11018	Crawford.....		
11019	do.....		
11020	do.....		
11021	do.....		
11022	do.....		
11023	do.....		
11024	do.....		
11025	do.....		
9859	Decatur.....		
10114	do.....		
11066	Dubois.....		
11182	Huntington.....		
9811	Jennings.....		
10834	do.....		
10847	do.....		
10256	Bloomington (east of).....		
10257	Bloomington.....		
10493	do.....		
9860	Greencastle.....		
10519	Filmore.....		
10520	do.....		
10727	Greencastle.....		
10020	Elbertfield.....		
9935	Bluffton.....		
10633	(2).....		
(2)	(2).....		
10694	(2).....		

KANSAS.

9599	Fort Scott (7 miles west of).....		
9780	Beloit.....		

Bourbon.....			
Mitchell.....			

¹ Test not made.² Exact locality not known.

TABLE I.—Results of physical tests of road-building rock from the United States, Canada, Porto Rico, and Cuba, from Jan. 1, 1916, to Jan. 1, 1917—Con.

KENTUCKY.

Serial No.	Town or city.	County.	Name of material.	Crushing strength, pounds per square inch.	Weight per cubic foot.	Absorption per cubic foot.	Per cent of wear.	French coefficient of wear.	Hardness.	Toughness.	Cementing value.
10134	Lexington.....	Fayette.....	Argillaceous limestone.....	(1)	Pounds, 168	Pounds, 0.19	6.1	6.6	16.0	4	41
10136	do.....	do.....	Limestone.....	(1)	168	.17	5.5	7.3	12.7	4	34
10451	Cerulean Springs (near).....	Trigg (2).....	Argillaceous limestone.....	(1)	167	.45	4.7	8.5	14.2	6	37
9829	(2).....	(3).....	(1)	165	1.31	(1)	(1)	13.7	6	30
9830	(3).....	(1)	165	.82	(1)	(1)	15.5	10	44

MAINE.

10219	North Jay.....	Franklin.....	Granite.....	21,260	164	0.84	2.7	14.8	19.3	7	13
9497	Mount Desert.....	Hancock.....	do.....	19,780	165	.21	3.4	11.8	19.7	9	11
10233	do.....	do.....	do.....	19,220	162	.90	4.1	9.8	18.7	8	9
10234	do.....	do.....	do.....	24,700	160	.67	3.2	12.5	18.7	12	14
10988	Ship Harbor.....	do.....	do.....	28,150	165	(1)	(1)	(1)	19.3	18	(1)
10989	do.....	do.....	do.....	26,500	163	.31	(1)	(1)	18.7	13	*
10990	do.....	do.....	do.....	32,450	164	.42	(1)	(1)	19.3	16	(1)
9781	St. George.....	Knox.....	do.....	18,780	(1)	(1)	(1)	(1)	19.3	16	(1)
9863	do.....	do.....	do.....	17,150	(1)	(1)	(1)	(1)	18.8	12	(1)
10019	Vinal Haven.....	Biotite granite.....	do.....	21,650	165	.25	3.1	12.9	19.3	14	28
9996	Long Cove.....	Granite.....	do.....	17,500	168	.23	3.3	12.1	19.2	10	30
10249	do.....	do.....	do.....	22,500	165	.86	3.0	13.3	19.3	13	(1)
10250	do.....	do.....	do.....	22,330	166	.82	3.5	11.4	19.3	8	(1)
9706	Rockland.....	Marble.....	do.....	(1)	175	.40	4.3	9.3	17.0	4	47

MARYLAND.

10105	Frederick.....	Frederick.....	Limestone.....	(1)	(1)	0.46	3.0	13.3	16.0	5	(1) 32
10021	North Laurel.....	Howard.....	Amphibolite.....	(1)	(1)	200	3.5	11.4	17.7	8	(1)
10101	Dickerson.....	Montgomery.....	Diabase (trap).....	(1)	(1)	42	1.4	28.6	18.5	21	(1)
11153	do.....	do.....	Biotite granite.....	(1)	171	66	3.1	12.9	18.7	13	(1)
11152	do.....	do.....	Epidote hornblende gneiss.....	(1)	198	66	3.1	12.9	16.0	11	(1)

MASSACHUSETTS.

10016	Great Barrington.....	Berkshire.....	Marble.....	175	0.37	5.6	7.1	15.3	4	43
10288	Otis.....	do.....	Granite.....	166	.71	2.6	18.0	9	(1)	24
9770	Fair River.....	Bristol.....	Biotite gneiss.....	178	.27	2.7	18.2	17	(1)	17
11017	Aeschnet.....	do.....	Chlorite gneiss.....	167	.44	2.4	16.6	19.0	(1)	17
10247	Seekonk.....	do.....	Feldspathic sandstone.....	167	.76	4.0	10.0	18.7	12	9
9649	Essex.....	do.....	Granite.....	165	.32	3.7	10.8	19.7	10	9
9650do.....	do.....	do.....	165	.35	4.4	9.1	19.7	10	17
9651do.....	do.....	do.....	22, 285	.33	4.9	8.2	19.3	7	13
9652do.....	do.....	do.....	18, 780	.21	3.6	11.1	19.3	11	13
10089	West Rutland.....	Worcester.....	do.....	164	.16	2.9	13.8	18.6	12	19
10090do.....	do.....	do.....	161	.79	6.7	6.0	18.0	7	18
10091do.....	do.....	Biotite gneiss.....	168	.89	6.5	6.2	16.3	9	35
10835	Fayville.....	do.....	Granite gneiss.....	162	.75	3.0	13.3	18.7	11	(1)

MICHIGAN.

9855	Marquette.....	Marquette.....	Hornblende gneiss.....	184	0.62	{1}	{1}	19.3	22	30
9857do.....	do.....	Amphibolite.....	184	.66	{1}	{1}	18.0	17	49
9856do.....	do.....	Allered diabase.....	181	.52	{1}	{1}	18.7	25	32
9875do.....	do.....	do.....	175	.42	2.1	19.1	19.3	12	27
9976do.....	do.....	do.....	184	.60	3.8	10.5	16.0	13	55
9977do.....	do.....	Dolomite.....	175	.64	3.1	12.9	18.3	11	97
9889	Monroe.....	Monroe.....	Argillaceous dolomite.....	165	3.03	3.6	11.1	17.0	16	30
9988do.....	do.....	do.....	175	4.2	9.5	{1}	5	22	22
9989do.....	do.....	Dolomite.....	172	1.47	4.7	8.5	13.5	5	27
10041do.....	do.....	Limestone.....	159	3.6	11.1	17.0	17	18	18
9888	Sibley.....	Wayne.....	do.....	159	2.82	12.4	3.2	15.3	6	44

MINNESOTA.

10485	Jasper.....	Rock.....	Quartzite.....	(1)	164	0.18	2.0	20.0	19.7	17	(1)
-------	-------------	-----------	----------------	-----	-----	------	-----	------	------	----	-----

MISSISSIPPI.

10287	(2).....	Holmes.....	Sandstone.....	{1}	144	4.70	7.8	5.1	18.0	8	(1)
10098	New Albany.....	Union.....	do.....	{1}	156	2.58	7.1	3.6	18.7	7	5

¹ Test not made.² Exact locality not known.

TABLE I.—Results of physical tests of road-building rock from the United States, Canada, Porto Rico, and Cuba, from Jan. 1, 1916, to Jan. 1, 1917—Con.

MISSOURI.

Serial No.	Town or city.	County.	Name of material.	Crushing strength, pounds per square inch.	Weight per cubic foot.	Absorption per cubic foot.	French coefficient of wear.	Hardness.	Toughness.	Cementing value.
10169	West Line.....	Cass.....	Limestone.....	(1)	Pounds.	Pounds.				
10410	(2) do.....	do.....		156	1.09	11.5	3.5	13.5	5	24
10251	Hamburg.....	St. Charles.....		107	.53	5.6	7.2	14.7	6	31
10252	do.....	do.....		167	.63	5.2	7.7	12.3	4	37
10237	Siroclair.....	do.....		104	.73	7.3	5.5	10.7	3	34
10238	do.....	do.....		167	.73	4.0	10.0	16.0	7	25
				167	.73	5.1	7.9	15.3	5	22

NEBRASKA.

9905	Nehawka.....	Cass.....	Argillaceous limestone.....	(1)	168	0.75	4.7	8.5	16.0	6	42
------	--------------	-----------	-----------------------------	-----	-----	------	-----	-----	------	---	----

NEW HAMPSHIRE.

9946	Fitzwilliam.....	Cheshire.....	Granite.....	26,100	165	0.32	3.7	10.8	17.7	9	15
9893	Marlboro.....	do.....		15,615	165	.36	6.7	6.0	17.3	8	18
9894	do.....	do.....		15,255	165	.52	5.7	7.0	19.3	6	23
9895	Fitzwilliam.....	do.....		10,825	165	.33	3.8	10.5	18.7	9	17
9994	Allentown.....	Merrimack.....		18,110	165	.61	2.5	16.0	19.0	11	23

NEW JERSEY.

10795	Lambertville.....	Hunterdon.....	Diabase.....	(1)	183	0.46	2.8	14.3	18.7	19	49
9921	Mount Hope.....	Morris.....	Pyroxene granite.....	(1)	178	.44	2.4	16.7	18.3	9	18
10472	Boundbrook.....	Somerset.....	Altered diabase.....	(1)	184	.06	2.2	18.2	18.7	30	54

NEW MEXICO.

	Silver City.....	Grant.....	Altered granite porphyry.....	(1)	156	1.73	3.4	11.8	18.6	18	(1)
978											
10097	Dolgeville.....	Herkimer.....	Dolomite.....	(1)	173	0.66	3.1	12.9	15.3	* 10	29
10236	Alexandria Bay.....	Jefferson.....	Biotite granite.....	(1)	163	(1)	2.8	14.3	18.7	12	(1)
10319	do.....	do.....	Granite.....	(1)	28,900	.49	1.4	18.0	10	10	12
10042	Albion.....	Orleans.....	Sandstone.....	(1)	20,000	(1)	3.4	11.8	17.3	9	(1)
10093	Rockland Lake.....	Rockland.....	Gabbroitic diabase.....	(1)	187	.19	3.0	13.3	19.0	13	29
10694	do.....	do.....	do.....	(1)	183	.27	3.6	11.1	19.0	12	67
10771	do.....	do.....	do.....	(1)	189	.23	3.0	13.3	18.7	12	37
10191	Hopkinton.....	St. Lawrence.....	Sandstone.....	(1)	157	2.02	2.8	14.3	18.0	12	7
11181	Tuscarora.....	Sullivan.....	Feldspathic sandstone.....	(1)	26,300	171	1.64	3.3	12.1	15.3	14
11182	Collisdon.....	do.....	do.....	(1)	22,620	166	1.04	3.0	13.3	14.7	13
10999	Pecskill (south of)	Westchester.....	Hyperssthene syenite.....	(1)	179	.62	3.5	11.4	17.0	9	(1)
11199	Yortown.....	do.....	Granite.....	(1)	16,200	168	.77	5.8	18.0	5	(1)

NEW YORK.

10193	Cranberry.....	Avery.....	Hornblende gneiss.....	(1)	208	0.70	4.3	9.3	(1)	(1)	18
10194	do.....	do.....	Biotite gneiss.....	(1)	192	.48	5.5	7.3	(1)	(1)	16
9858	Ashville.....	Buncombe.....	do.....	(1)	168	.26	4.4	9.1	19.3	7	33
10972	do.....	do.....	do.....	(1)	168	1.35	2.7	14.8	18.0	13	(1)
10073	(1).....	Rowan.....	do.....	(1)	172	.67	3.7	11.4	18.0	13	(1)
9892	Granite Quarry (near)	do.....	Granite.....	(1)	21,25	(1)	4.6	8.7	(1)	(1)	13
10306	Granite Quarry (near)	do.....	do.....	(1)	34,860	164	.22	2.0	20.0	18.7	10
10405	Granite Quarry.....	do.....	do.....	(1)	164	(1)	(1)	(1)	10	10	(1)
10412	(2).....	do.....	do.....	(1)	51	.51	2.8	14.3	19.3	9	(1)
10413	(3).....	do.....	do.....	(1)	162	.43	3.3	12.1	19.0	7	(1)
10770	(2).....	do.....	do.....	(1)	164	.43	5.2	7.7	19.3	10	(1)
9897	(2).....	do.....	do.....	(1)	162	.55	13.8	2.9	(1)	(1)	14

NORTH CAROLINA.

10193	Lima.....	Allen.....	Dolomite.....	(1)	165	2.67	3.2	12.5	14.7	7	(1)
10025	do.....	do.....	Archaean limestone.....	(1)	168	2.77	3.5	11.4	14.7	12	31
10026	do.....	do.....	do.....	(1)	168	1.96	3.7	10.8	16.0	11	33
10027	do.....	do.....	do.....	(1)	168	2.26	3.6	11.1	15.0	11	34
10305	do.....	do.....	Limestone.....	(1)	169	1.80	4.2	9.5	16.0	6	27
9933	Middletown.....	Butler.....	Basic open-hearth slag.....	(1)	209	2.33	4.1	9.8	(1)	(1)	471
9954	do.....	do.....	do.....	(1)	190	2.74	20.4	1.7	(1)	(1)	191

OHIO.

9864	Lima.....	Allen.....	Dolomite.....	(1)	165	2.67	3.2	12.5	14.7	7	(1)
10025	do.....	do.....	Archaean limestone.....	(1)	168	2.77	3.5	11.4	14.7	12	31
10026	do.....	do.....	do.....	(1)	168	1.96	3.7	10.8	16.0	11	33
10027	do.....	do.....	do.....	(1)	168	2.26	3.6	11.1	15.0	11	34
10305	do.....	do.....	Limestone.....	(1)	169	1.80	4.2	9.5	16.0	6	27
9933	Middletown.....	Butler.....	Basic open-hearth slag.....	(1)	209	2.33	4.1	9.8	(1)	(1)	471
9954	do.....	do.....	do.....	(1)	190	2.74	20.4	1.7	(1)	(1)	191

¹ Test not made.² Exact locality not known.

TABLE I.—*Results of physical tests of road-building rock from the United States, Canada, Porto Rico, and Cuba, from Jan. 1, 1916, to Jan. 1, 1917*—Con.

OHIO—Continued.

Serial No.	Town or city.	County.	Name of material.	Crushing strength, pounds per square inch.	Weight per cubic foot.	Absorption per cubic foot.	Pounds.	French coefficient of wear.	Hardness.	Toughness.	Cementing value.
10516	Farmer.....	Clinton.....	Limestone.....	(1)	156	5.2	7.6	13.2	4	36	
10517	do.....	do.....	Siliceous limestone.....	(1)	167	4.9	6.6	13.7	5	45	
10536	Marble Cliff.....	Franklin.....	Argillaceous limestone.....	(1)	167	(1)	15.2	6	27		
9883	North Baltimore (Wood County, near).	Henry.....	Argillaceous dolomite.....	(1)	168	2.61	5.0	16.0	10	44	
11198	Bellevue.....	Huron.....	Dolomite.....	(1)	156	4.89	4.9	8.2	6.0	5	52
9854	Ironton.....	Lawrence.....	Blast-furnace slag.....	(1)	181	7.73	5.8	16.0	6	21	
9890	Waterville.....	Lucas.....	Argillaceous dolomite.....	(1)	168	2.36	3.3	12.1	16.3	11	47
9983	do.....	do.....	Dolomite.....	(1)	168	2.04	2.8	14.3	16.3	14	38
11097	White House.....	Miami.....	Siliceous limestone.....	(1)	161	2.90	6.2	6.5	9.3	6	41
10337	Pluma.....	do.....	Dolomite.....	(1)	156	2.33	10.3	3.9	11.0	4	35
10338	do.....	Montgomery.....	do.....	(1)	178	.97	4.8	8.3	15.0	13	30
10332	Centerville.....	Argillaceous limestone.....	do.....	(1)	(1)	(1)	(1)	(1)	(1)	3	
10333	do.....	do.....	do.....	(1)	(1)	(1)	(1)	(1)	(1)	5	24
10535	do.....	Ottawa.....	Dolomite.....	(1)	13,360	175	41	5.4	10.9	3	37
9945	Rocky Ridge.....	do.....	do.....	(1)	162	(1)	5.5	7.4	12.0	9	
9973	Limestone.....	Pebble.....	do.....	(1)	167	1.12	1.12	7.3	12.0	7	38
10339	New Paris.....	Wood.....	do.....	(1)	162	3.68	3.4	11.8	16.2	6	37
10346	Luckey.....	do.....	do.....	(1)	165	1.38	7.5	5.5	12.0	6	38
9947	Bowling Green.....	do.....	do.....	(1)	168	2.08	4.0	10.0	14.3	6	33
9957	North Baltimore.....	do.....	do.....	(1)						14	50

PENNSYLVANIA.

9786	Granite.....	Adams.....	Gabbroitic diabase.....	(1)	23,435	(1)	(1)	1.7	(1)	15.2	14
10104	Berks.....	Berks.....	Diabase.....	(1)	(1)	(1)	(1)	2.5	18.7	13	
10357	(2)....Connelville.	Delaware.....	Biotite gneiss.....	(1)	(1)	(1)	(1)	2.8	18.0	9	
9773	Fayette.....	Fayette.....	Siliceous limestone.....	(1)	168	0	46	14.3	17.7	13	85
10518	Montoursville.....	Lycoming.....	Argillaceous limestone.....	(1)	23,460	168	10	6.6	6.1	16.2	27
10677	Jersey Shore.....	do.....	Siliceous limestone.....	(1)	166	144	2.6	15.4	18.2	9	53
10137	Northampton.....	do.....	Blast-furnace slag.....	(1)	145	4.32	9.3	4.3	13.7	3	
10429	South Bethlehem.....	do.....	Quartzite.....	(1)	163	.53	3.3	12.1	19.0	13	
3812	Mount Carmel.....	Philadelphia.....	Biotite gneiss.....	(1)	165	.58	(1)	19.0	7		
11190	Holmesburg.....	Pike.....	Feldspathic sandstone.....	(1)	170	.63	12.5	16.7	12		
10345	Shohola.....	Confluence.....	Calcareous sandstone.....	(1)	168	.34	3.6	11.1	16.7	7	

RHODE ISLAND.

10171	Lincoln.....	Providence.....	Granite gneiss.....	170	0.17	3.9	10.3	18.7	12	20
10248	East Providence.....	do.....	Feldspathic sandstone.....	168	.59	3.6	11.1	18.0	12	16
10467	Westerly.....	Washington.....	Granite.....	161	.37	3.9	10.3	18.7	9	(1)

SOUTH CAROLINA.

10531	Rion.....	Fairfield.....	Biotite granite.....	165	0.59	4.4	9.1	18.3	8	(1)
10131	Greenville (17 miles from).....	Greenville.....	Granite.....	165	.82	4.4	9.1	18.7	8	5
10129	Greenville.....	do.....	Hornblende gneiss.....	172	.68	8.0	5.0	17.0	17	(1)
10130	Beverly.....	Pickens.....	Biotite gneiss.....	166	.75	4.1	9.8	17.7	4	20

SOUTH DAKOTA.

10108	Dell Rapids.....	Minnehaha.....	Quartzite.....	165	0.41	2.8	14.3	19.3	17	5
10894	Sioux Falls.....	do.....	do.....	163	.27	1.4	28.6	19.3	17	(1)
10895	do.....	do.....	Olivine diabase.....	190	.37	2.7	14.8	18.7	18	16
10896	Rowena.....	do.....	Quartzite.....	164	.28	2.7	14.8	19.3	17	(1)

TENNESSEE.

9902	Maryville.....	Blount.....	Argillaceous limestone.....	168	0.40	3.8	10.5	16.7	6	49
9933	do.....	do.....	Siliceous limestone.....	168	.30	4.3	9.3	16.7	5	39
10292	New Fazwell.....	Claiborne.....	do.....	171	1.84	4.2	9.5	13.3	8	31
10326	Harrigale (near).....	do.....	Dolomite.....	174	.92	3.2	12.5	16.0	14	19
10327	Harrigale.....	do.....	do.....	171	1.86	3.6	11.1	13.3	7	21
10446	New Fazwell (near).....	do.....	do.....	172	1.20	4.1	9.8	15.3	9	42
10561	New Fazwell.....	do.....	Siliceous dolomite.....	170	1.93	4.1	9.8	15.2	9	18
10483	James town.....	Fentress.....	Sandstone.....	145	3.97	10.8	3.7	16.0	4	(1)
9887	do.....	Knox.....	do.....	178	.20	4.1	9.8	16.0	11	49
10315	Mascot.....	Madisonville.....	Ferruginous sandstone.....	178	.41	4.0	10.0	17.3	8	(1)
10316	do.....	do.....	Siliceous limestone.....	169	.46	6.3	6.4	16.7	9	29
10317	do.....	do.....	Limestone.....	167	.77	8.3	4.8	16.7	9	33
10318	do.....	do.....	do.....	171	.33	4.2	9.5	17.3	8	26
10414	do.....	do.....	Crystalline limestone.....	168	.33	6.0	6.6	13.3	5	49
(2)	do.....	Pickett.....	Siliceous dolomite.....	174	1.36	3.3	12.1	15.7	18	29
9734	(2).....	Pickett.....	Argillaceous dolomite.....	168	2.65	4.3	9.3	13.2	12	55

¹ Test not made.² Exact locality not known.

TABLE I.—Results of physical tests of road-building rock from the United States, Canada, Porto Rico, and Cuba, from Jan. 1, 1916, to Jan. 1, 1917—Continued.

TEXAS.

Serial No.	Town or city.	County.	Name of material.	Crushing strength, pounds per square inch.	Weight per cubic foot.	Absorption per cubic foot.	Per cent of wear.	French coefficient of wear.	Hardness.	Toughness.	Cementing value.
				(1)	Pounds. 134	Pounds. 12,80	(1)	(1)	(1)	(1)	(1)
10044 (2).....	Burlington.....	Chittenden.....	Siliceous dolomite.....	163	0.26	3.7	11.1	16.7	13	38	
11191 Derby.....	Orleans.....	Clay limestone.....	Siliceous limestone.....	171	.46	3.0	13.3	17.3	9	96	
9673 Barre.....	Washington.....	Biotite granite.....	165	.37	2.8	14.3	19.0	9	9	19	

VERMONT.

Serial No.	Town or city.	County.	Name of material.	Crushing strength, pounds per square inch.	Weight per cubic foot.	Absorption per cubic foot.	Per cent of wear.	French coefficient of wear.	Hardness.	Toughness.	Cementing value.
				(1)	Pounds. 134	Pounds. 12,80	(1)	(1)	(1)	(1)	(1)
10848	Burlington.....	Chittenden.....	Siliceous dolomite.....	163	0.26	3.7	11.1	16.7	13	38	
11191 Derby.....	Orleans.....	Clay limestone.....	Siliceous limestone.....	171	.46	3.0	13.3	17.3	9	96	
9673 Barre.....	Washington.....	Biotite granite.....	165	.37	2.8	14.3	19.0	9	9	19	

VIRGINIA.

Serial No.	Town or city.	County.	Name of material.	Crushing strength, pounds per square inch.	Weight per cubic foot.	Absorption per cubic foot.	Per cent of wear.	French coefficient of wear.	Hardness.	Toughness.	Cementing value.
				(1)	Pounds. 134	Pounds. 12,80	(1)	(1)	(1)	(1)	(1)
9928 (2).....	Albemarle.....	Albemarle.....	Biotite gneiss.....	175	1.62	5.3	7.5	17.6	7	47	
9927 (2).....	do.....	do.....	Hornblende gneiss.....	193	.98	3.5	11.4	16.3	9	63	
9926 (2).....	do.....	do.....	Biotite gneiss.....	181	.75	3.1	7.8	18.7	5	24	
10253 Charlottesville.....	do.....	do.....	Granite gneiss.....	171	.75	5.4	7.4	17.3	5	48	
10172 Clifton Forge.....	do.....	do.....	Quartzite limestone.....	166	2.5	12.0	12.0	17.6	10	8	
9891 Lone Jack Station	do.....	do.....	Quartzite schist.....	159	1.34	3.3	3.3	(1)	(1)	5	
9904 Lynchburg.....	do.....	do.....	Apophite granite.....	165	.53	5.4	7.4	18.7	(1)	5	
10344 Carroll.....	do.....	do.....	Quartzite.....	25,885	1.20	4.3	9.3	18.6	14	31	
98119 Cliff View.....	do.....	do.....	Hornblende schist.....	184	.71	4.4	9.1	18.3	14	109	
9820 do.....	do.....	do.....	Altered hornblende gneiss.....	181	1.60	15.8	2.5	14.3	5	44	
10115 Boston.....	Culpeper	do.....	Altered rhyolite.....	168	.84	4.7	8.5	19.0	5	120	
99019 Warrenton.....	Fauquier	do.....	Amphibolite.....	187	4.6	8.7	(1)	(1)	(1)	43	
9900 do.....	do.....	do.....	do.....	181	2.44	5.9	6.7	(1)	(1)	17	
9870 do.....	do.....	do.....	do.....	187	1.46	3.6	11.1	(1)	(1)	27	
10304 do.....	do.....	do.....	do.....	185	.63	3.5	11.4	14.7	11	35	
10609 Hamilton (4 mile east of).....	Loudoun	do.....	Amphibolite.....	178	.49	3.9	10.3	17.3	10	10	
10099 Luray.....	Page	do.....	Argillaceous limestone.....	167	.75	5.4	7.4	14.3	5	35	
10298 Buckland.....	Prince William	do.....	do.....	178	1.75	(1)	9.7	17.3	(1)	13	
10430 Gate.....	Scots	do.....	do.....	168	.38	4.1	19.0	16.0	10	10	
10780 Wise.....	Wise	do.....	do.....	158	2.10	4.5	8.8	18.7	(1)	10	

WASHINGTON.

	10239 Cook (3 miles north of).....	Skamania.....	Basalt.....	(1)	177	0.92	2.6	15.4	18.3	24	14
WEST VIRGINIA.											
Dolomite.....											
10064 Martinsburg (south of).....	Berkley.....	Dolomite.....	(1)	178	0.31	3.6	11.1	16.3	10	29	
10069 Butts Store (west of).....	do.....	Feldspathic sandstone.....	(1)	140	3.45	7.2	18.7	18.7	(1)	8	
10073 Hedgeville (west of).....	do.....	Sandstone.....	(1)	165	.62	2.8	16.7	16.7	(1)	61	
10087 Tomahawk (north of).....	do.....	Limestone.....	(1)	156	1.66	7.9	5.1	5.1	(1)	23	
10082 Inwood (near).....	do.....	Argillaceous limestone.....	(1)	144	3.19	16.6	2.4	19.3	(1)	17	
10062 Ferrel ridge.....	do.....	Limestone.....	(1)	168	1.61	6.2	6.5	14.0	4	56	
10063 Blairton (near).....	do.....	Siliceous limestone.....	(1)	168	.19	5.1	7.8	16.7	6	28	
10065 Berkeley Station.....	do.....	Argillaceous limestone.....	(1)	168	.27	6.3	6.4	16.7	4	34	
10066 Jones Spring.....	do.....	Limestone.....	(1)	168	.31	4.4	9.1	17.3	9	44	
10068 Bedington (east of).....	do.....	Argillaceous limestone.....	(1)	172	.19	4.9	8.2	16.0	10	33	
10070 Bunker Hill.....	do.....	Limestone.....	(1)	168	.24	5.1	7.8	16.0	4	34	
10071 Nipetown.....	do.....	do.....	(1)	168	.43	4.9	8.2	16.0	3	32	
10072 Spring Mills.....	do.....	Argillaceous limestone.....	(1)	168	.27	4.2	9.5	15.9	4	45	
10074 Gerrardstown.....	do.....	do.....	(1)	172	.46	6.5	6.2	15.7	(1)	22	
10075 Bedford (east of).....	do.....	Argillaceous limestone.....	(1)	168	.56	7.1	10.1	17.0	(1)	29	
10076 Van Cleveville (south of).....	do.....	Limestone.....	(1)	168	.36	5.0	8.0	17.0	9		
10077 Darksville.....	do.....	Siliceous limestone.....	(1)	168	.31	5.0	8.0	15.0	4		
10078 Tomahawk.....	do.....	Limestone.....	(1)	168	.27	4.5	8.9	18.3	15		
10079 Falling Water.....	do.....	Argillaceous limestone.....	(1)	168	1.27	4.7	8.5	16.7	8		
10080 Little Georgetown.....	do.....	Crystalline limestone.....	(1)	175	.37	6.5	6.2	18.7	10		
10081 Jones Spring.....	do.....	Crystalline limestone.....	(1)	168	.37	5.7	7.0	14.0	4		
10082 Falling Water (near).....	do.....	Limestone.....	(1)	168	.59	5.6	7.1	17.0	(1)		
10083 Falling Water.....	do.....	Chert and limestone (mixed).....	(1)	168	1.47	8.5	10.5	16.3	(1)	25	
10084 Blairton.....	do.....	Limestone.....	(1)	168	.23	5.9	6.8	16.3	5		
10085 Cumblo.....	do.....	do.....	(1)	172	.52	4.6	8.7	16.7	4		
10086 Martinsburg (south of).....	do.....	Argillaceous limestone.....	(1)	168	.56	5.8	6.9	16.7	5		
10102 Martinsburg.....	do.....	do.....	(1)	166	.60	5.4	7.4	16.7	6		
10511 Scherr.....	do.....	Argillaceous limestone.....	(1)	168	.66	3.8	10.5	16.3	(1)	31	
9925 Renick.....	do.....	Limestone.....	(1)	168	.24	4.1	9.8	15.7	8		
9927 Fort Spring.....	do.....	Argillaceous limestone.....	(1)	168	2.7	14.8	11.0	11.0	6		
16103 Kearnyville.....	do.....	Monongalia.....	(1)	168	.73	4.7	8.5	15.7	8		
9966 Greer.....	do.....	do.....	(1)	168	.59	4.7	8.5	15.7	9		
9967 do.....	do.....	do.....	(1)	168	.73	4.8	8.3	14.0	9		
9968 do.....	do.....	Siliceous limestone.....	(1)	168	.56	3.0	13.3	16.7	10		
9969 do.....	do.....	Preston.....	(1)	154	1.88	8.1	4.9	17.3	5		
10348 Albright (near).....	do.....	Sandstone.....	(1)	160	2.40	8.0	10.0	15.3	9		
10349 Albright.....	do.....	Ferruginous sandstone.....	(1)	154	3.69	3.9	10.3	10.6	9		
11130 Trap Hill District.....	Raleigh.....	Sandstone.....	(1)	154	3.69	3.9	12.3	3.3	8.7		
10036 Spencer (near).....	Roane.....	Feldspathic sandstone.....	(1)	156	3.52	12.3	10.8	14.3	10		
10509 Davis.....	Tucker.....	Siliceous limestone.....	(1)	167	.05	3.7	12.0	14.3	30		
10510 do.....	do.....	Argillaceous limestone.....	(1)	168	.12	5.0	8.0	16.3	6		

¹ Test not made.² Exact locality not known.

TABLE I.—Results of physical tests of road-building rock from the United States, Canada, Porto Rico, and Cuba, from Jan. 1, 1916, to Jan. 1, 1917—Con.

WISCONSIN.

Serial No.	Town or city.	County.	Name of material.	Crushing strength, pounds per square inch.	Weight per cubic foot.	Absorption per cubic foot.	French coefficient of wear.	Hardness.	Toughness.	Cementing value.
9999	Berlin.....	Green Lake.....	Rhyolite.....	(1)	Pounds.	Pounds.	0.16	21.3	19.0	15
10108	Buffalo.....	Marquette.....	Altered syenite.....	(1)	165	0.13	2.2	18.2	30	13
10014	Wauwatosa.....	Milwaukee.....	Argillaceous dolomite.....	(1)	167	2.11	3.7	2.8	14.7	8
11129	do.....	do.....	do.....	(1)	168	2.01	3.8	10.5	15.3	11
10036	Wells.....	Monroe.....	Calcareous sandstone.....	(1)	168	2.01	3.8	8.3	18.0	5
9970	Black Creek.....	Outagamie.....	Dolomite.....	(1)	162	2.79	4.8	8.7	14.7	9
9971	do.....	do.....	do.....	(1)	178	.58	4.6	8.7	15.3	31
10022	Belgium.....	Ozaukee.....	Argillaceous dolomite.....	(1)	178	.63	4.1	9.8	14.3	8
10159	Grand Rapids.....	Wood.....	Sandstone.....	(1)	175	1.15	7.4	5.5	18.3	5
10028	(2).....	Wood.....	Dolomite.....	(2)	168	1.91	3.3	12.1	13.3	3
							1.05	7.1	5.6	41

CANADA.

10017	Montreal.....	Province of Quebec.....	Nephelite syenite.....	156	0.60	2.2	18.2	18.7	18	22
10332	Wellesley Island.....	do.....	Biotite granite.....	165	.28	2.9	13.8	18.0	10	10
9746	Welland.....	Province of Ontario.....	Cherty limestone.....	165	.41	3.9	10.3	18.3	13	13

¹ Test not made.² Exact locality not known.

TABLE II.—*Results of compression tests of rock complete to January 1, 1917.*

ARKANSAS.

Serial No.	Locality.	County.	Name.	Crushing strength, pounds per square inch.
9828	Lamar.....	Johnson.....	Feldspathic sandstone.....	21,980
6331	Bald Knob.....	White.....	Sandstone.....	19,860

CONNECTICUT.

9791	Oneco.....	Windham.....	Biotite granite.....	16,635
11098do.....do.....do.....	23,290
11099do.....do.....	Gneissoid granite.....	20,200

GEORGIA.

10381	Southeast side Kennesaw Mountain.....	Cobb.....	Feldspathic gneiss.....	18,500
10382	Marietta, 4 miles southwest of.....do.....	Biotite gneiss.....	14,000
10389	Austell, $\frac{1}{2}$ mile west.....do.....	Granite gneiss.....	12,890
10393	Blackwell Station, 1 mile north of.....do.....	Hornblende gneiss.....	17,350

ILLINOIS.

4422	Embaras.....	Coles.....	Limestone.....	17,300
5509	Thornton.....	Cook.....	Dolomite.....	23,060
6053do.....do.....do.....	16,880
8711	Hillside.....do.....	Argillaceous dolomite.....	15,730
4660	Tunnel Hill.....	Johnson.....	Sandstone.....	19,150
7509	Reevesville.....do.....	Argillaceous limestone.....	25,780
7510do.....do.....do.....	28,400
4764	Kankakee.....	Kankakee.....	Dolomite.....	20,610
5550do.....do.....do.....	17,710
6088do.....do.....	Argillaceous dolomite.....	20,830
6165do.....do.....	Dolomite.....	11,660
6865do.....do.....do.....	13,500
7298do.....do.....	Argillaceous dolomite.....	25,850
7299do.....do.....do.....	20,000
7300do.....do.....do.....	19,800
7301do.....do.....do.....	19,700
7302do.....do.....	Dolomite.....	17,050
7871	Lehigh.....do.....	Argillaceous dolomite.....	16,700
10367	Kankakee.....do.....	Dolomite.....	11,180
4421	Alton.....	Madison.....	Limestone.....	15,100
7422	Brookville.....	Ogle.....	Argillaceous dolomite.....	18,640
7423do.....do.....do.....	18,180
5549	Anna.....	Union.....	Limestone.....	19,510
9827	Joliet.....	Will.....	Dolomite.....	8,130

INDIANA.

5534	Logansport.....	Cass.....	Limestone.....	20,350
4655	Greensburg.....	Decatur.....	Dolomite.....	17,960
4658	St. Paul.....do.....	Limestone.....	18,400
4659do.....do.....	Domitic limestone.....	20,510
4690	Westport.....do.....do.....	20,000
5088	St. Paul.....do.....	Limestone.....	19,800
11183	Huntington.....	Huntington.....	Dolomite.....	25,420
4197	Mitchell.....	Lawrence.....	Argillaceous dolomite.....	12,250
5027	Bedford.....do.....	Limestone.....	6,900
5029do.....do.....do.....	6,450
3368	Greencastle.....	Putnam.....do.....	16,000
5737	Osgood.....	Ripley.....do.....	14,470
4657	Wabash.....	Wabash.....	Dolomitic limestone.....	18,790

TABLE II.—*Results of compression tests of rock complete to Jan. 1, 1917—Continued.*

IOWA.

Serial No.	Locality.	County.	Name.	Crushing strength, pounds per square inch.
5525	Cedar Rapids.....	Linn.....	Dolomitic limestone.....	19,950
5526	La Grande.....	Marshall.....	do.....	14,850

KANSAS.

9599	Fort Scott (7 miles west).....	Bourbon.....	Limestone breccia	7,380
------	--------------------------------	--------------	-------------------------	-------

KENTUCKY.

5552	Princeton.....	Caldwell.....	Dolomitic limestone.....	23,860
7688	Cedar Bluff.....	do.....	Argillaceous limestone.....	25,720
5921	Limestone.....	Carter.....	Limestone.....	14,900
5922	Carter.....	do.....	Siliceous limestone.....	13,400

MAINE.

10219	North Jay.....	Franklin.....	Granite.....	21,260
7438	Swan's Island.....	Hancock.....	Biotite granite.....	18,400
9997	Somes Sound, Mount Desert Islands.....	do.....	Granite.....	19,780
10233	do.....	do.....	do.....	19,220
10234	do.....	do.....	do.....	24,700
10988	Ship Harbor.....	do.....	do.....	28,650
10989	do.....	do.....	do.....	26,500
10990	do.....	do.....	do.....	32,450
8745	Vinal Haven.....	Knox.....	do.....	20,020
8768	St. George.....	do.....	do.....	22,800
8769	Vinal Haven.....	do.....	do.....	20,920
9781	St. George.....	do.....	do.....	18,780
9865	do.....	do.....	do.....	17,150
9996	Long Cove.....	do.....	do.....	17,540
9445	Vinal Haven.....	do.....	Biotite granite.....	21,220
10249	Long Cove.....	do.....	do.....	22,500
10250	do.....	do.....	Granite.....	22,330
10366	St. George.....	do.....	do.....	27,050
10019	Vinal Haven.....	do.....	Biotite granite.....	21,650
7439	Frankford.....	Waldo.....	do.....	20,600

MARYLAND.

5611	Mount Savage Junction.....	Allegany.....	Siliceous limestone.....	34,930
4884	Frederick.....	Frederick.....	Limestone.....	17,580
5694	Havre de Grace.....	Harford.....	Gneissoid granite.....	34,410
5695	do.....	do.....	Sericite gneiss.....	20,090
5696	do.....	do.....	Gneissoid granite.....	21,670
5697	do.....	do.....	Amphibolite.....	34,380
5698	do.....	do.....	Gneissoid granite.....	35,210
5699	do.....	do.....	do.....	22,190

MASSACHUSETTS.

10288	Otis.....	Berkshire.....	Granite.....	18,260
6891	Rockport.....	Essex.....	Biotite granite.....	22,370
6892	do.....	do.....	do.....	23,610
6893	do.....	do.....	do.....	22,570
6894	do.....	do.....	do.....	21,600
8796	do.....	do.....	do.....	23,830
9649	Gloucester.....	do.....	Granite.....	19,580
9650	do.....	do.....	do.....	18,130
9651	Rockport.....	do.....	do.....	22,390
9652	do.....	do.....	do.....	18,780
5671	Westfield.....	Hampden.....	Altered diabase.....	32,850

TABLE II.—*Results of compression tests of rock complete to Jan. 1, 1917—Continued.*
MASSACHUSETTS—Continued.

Serial No.	Locality.	County.	Name.	Crushing strength, pounds per square inch.
8862	Westford.....	Middlesex.....	Granite.....	13,980
8874do.....do.....do.....	17,000
8875do.....do.....do.....	16,250
5988	West Auburn.....	Worcester.....	Mica gneiss.....	21,950

MICHIGAN.

9988	Monroe.....	Monroe.....	Argillaceous dolomite.....	11,750
9593	Calcite.....	Presque Isle.....	Limestone.....	10,300

MINNESOTA.

5524	Stockton.....	Winona.....	Argillaceous dolomite.....	16,000
------	---------------	-------------	----------------------------	--------

MISSOURI.

6375	Rochefort.....	Boone.....	Limestone.....	13,900
10169	West Line.....	Cass.....do.....	16,690
6377	Sweeney.....	Cooper.....	Argillaceous limestone.....	14,900

NEW YORK.

6457	(1).....	Clinton.....	Plagioclase gneiss.....	18,500
6458	(1).....do.....	Pyroxene gneiss.....	20,500
8011	(1).....	Dutchess.....	Dolomite.....	34,450
5544	Camelo.....do.....do.....	29,050
5872	Akron Junction.....	Erie.....	Cherty limestone.....	16,700
8577	Gloversville.....	Fulton.....	Biotite gneiss.....	14,585
4157	Alexandria Bay.....	Jefferson.....	Granite.....	21,600
8833do.....do.....do.....	26,180
8902do.....do.....do.....	14,150
9129do.....do.....do.....	14,390
9130do.....do.....	Gneissoid granite.....	17,600
7437do.....do.....	Granite.....	27,200
10236do.....do.....	Biotite granite.....	28,130
10042	Albion.....	Orleans.....	Sandstone.....	29,000
8012do.....	Rockland.....	Gabbroitic diabase.....	31,300
8013	(1).....do.....	Siliceous dolomite.....	22,200
10191	Hopkinton.....	St. Lawrence.....	Sandstone.....	35,240
11182	Callicoon.....	Sullivan.....	Feldspathic sandstone.....	22,620
11181	Tusten.....do.....do.....	26,300
11199	Yorktown.....	Westchester.....	Granite.....	16,200

NEW HAMPSHIRE.

9893	Marlboro.....	Cheshire.....	Granite.....	15,615
9894do.....do.....do.....	15,250
9895	Fitzwilliam.....do.....do.....	10,830
9946	(1).....do.....do.....	26,100
8872	Melford.....	Hillsboro.....do.....	15,050
9010do.....do.....	Biotite granite.....	16,640
9011do.....do.....do.....	14,870
9012do.....do.....do.....	18,230
9031	Concord.....	Merrimack.....	Granite.....	16,600
9036do.....do.....do.....	13,420
9037do.....do.....do.....	13,900
8870do.....do.....do.....	15,100
9994	Allentown.....do.....do.....	18,110

¹ Exact locality not known.

TABLE II.—*Results of compression tests of rock complete to Jan. 1, 1917—Continued.*

NORTH CAROLINA.

Serial No.	Locality.	County.	Name.	Crushing strength, pounds per square inch.
8396	(1).	Forsythe	Granite.....	13,140
8397	(1).	do	Hypersthene gabbro.....	11,880
8682	Spencer Mountain.	Gaston.	Feldspathic quartzite.....	31,520
8881	Gastonia.	do	Quartzite.....	17,100
8576	Mooresville.	Iredell.	Biotite granite.....	26,000
5373	(1).	McDowell.	Sandstone.....	22,600
9038.	Wilson.	Wilson.	Granite.....	16,070
5956	Stacey.	Rockingham.	Granite gneiss.....	23,220
5496	Samsbury.	Rowan.	Granite.....	33,750
9892	Granite Quarry.	do	do.....	21,130
10306	Granite Quarry (near).	do	do.....	34,860
10412	(1).	do	do.....	20,930
10413	(1).	do	do.....	23,580
10770	(1).	do	do.....	17,800
11200	(1).	do	do.....	26,400
6071	Bostic.	Rutherford.	Biotite gneiss.....	16,100
5497	Mount Airy.	Surry.	Granite.....	18,400
7433	do.	do	do.....	15,200
8901	do.	do	do.....	5,100
9048	do.	do	do.....	16,440
8419	Granita (near).	Wake.	Biotite granite.....	14,160
3807	Wise.	Warren.	Granite.....	18,240
3808	do.	do	do.....	18,560
5374	(1).	Yancey.	Quartzite.....	12,900

OHIO.

4694	Osborne.	Clarke.	Dolomitic limestone.....	8,690
4695	Springfield.	do	Dolomite.....	18,960
9282	Cleveland.	Cuyahoga.	Granite.....	31,790
9283	do.	do	do.....	27,900
9284	do.	do	do.....	24,790
9285	do.	do	do.....	26,990
9459	do.	do	do.....	24,900
4378	Sandusky.	Erie.	Limestone.....	19,400
5554	do.	do	do.....	21,850
5753	Castalia.	do	Dolomitic limestone.....	18,530
6055	do.	do	Limestone.....	20,810
6056	Akron Junction.	do	Cherty limestone.....	31,180
5505	Marble Cliff.	Fran'l'lin	Limestone.....	16,750
5506	do.	do	do.....	12,350
5630	Columbus.	do	Ferruginous sandstone.....	21,800
4693	Patterson.	Hardin.	Dolomite.....	11,360
5553	Dunkirk.	do	do.....	26,200
4707	Hillsboro.	Highland.	Cherty limestone.....	15,590
8347	Clarksfield.	Huron.	Calcareous sandstone.....	9,490
4656	Big Springs.	Logan.	Argillaceous limestone.....	16,380
6054	Vulcan.	Lucas.	Siliceous limestone.....	25,480
6057	Holland.	do	Argillaceous limestone.....	19,430
8402	Toledo, 10 miles west of.	do	Dolomite.....	11,600
10537	Piqua.	Miami.	do.....	9,810
10538	do.	do	do.....	15,150
6052	White Rock.	Ottawa.	do.....	16,620
9945	Rocky Ridge.	do	do.....	13,3 0
10539	New Paris.	Preble.	do.....	16,480
5556	Bloomville.	Seneca.	Limestone.....	20,250
5555	Middleport.	Van Wert.	Dolomite.....	25,200

OKLAHOMA.

3388	Granite.....	Greer.....	Granite.....	18,000
------	--------------	------------	--------------	--------

PENNSYLVANIA.

9786	Granite.....	Adams.	Gabbroitic diabase.....	23,440
5602	Hyndman.	Bedford.	Impure limestone.....	24,150
5603	do.	do	Siliceous limestone.....	21,860
5632	Birdsboro.	Berks.	Altered diabase.....	39,215

¹ Exact locality not known.

TABLE II.—*Results of compression tests of rock complete to Jan. 1, 1917—Continued.*
PENNSYLVANIA—Continued.

Serial No.	Locality.	County.	Name.	Crushing strength, pounds per square inch.
8724	Juniata.....	Blair.....	Argillaceous limestone.....	15,480
8725	(1).....do.....do.....	20,880
8625	Hazard.....	Carbon.....	Blast-furnace slag.....	9,000
7973	(1).....	Chester.....	Pyroxene quartzite.....	31,800
7978	(1).....do.....	Mica schist.....	23,500
7979	(1).....do.....do.....	23,900
5578	Salona.....	Clinton.....	Argillaceous limestone.....	18,710
7844	(1).....	Dauphin.....	Siliceous limestone.....	26,500
8306	(1).....do.....	Limestone.....	8,510
8427	(1).....do.....do.....	19,250
8465	(1).....do.....	Siliceous dolomite.....	9,640
8049	(1).....	Elk.....	Ferruginous sandstone.....	14,150
5771	Indian Creek Station.....	Fayette.....	Calcareous sandstone.....	37,740
6097	Bidwell.....do.....	Limestone.....	13,450
9347	Connellsburg.....do.....do.....	26,050
5604	Water Street.....	Huntingdon.....	Feldspathic sandstone.....	22,330
5557	Walford.....	Lawrence.....	Limestone.....	27,500
10518	Montoursville.....	Lycoming.....	Argillaceous limestone.....	23,460
10672	Jersey Shore.....do.....	Siliceous limestone.....	20,360
6153	Porter Township.....do.....	Argillaceous limestone.....	28,580
6154do.....do.....do.....	26,860
6155do.....do.....do.....	18,610
6156do.....do.....do.....	22,930
6157do.....do.....	Limestone.....	21,900
6158do.....do.....do.....	14,160
7980	Port Allegheny.....	McKean.....	Feldspathic sandstone.....	9,680
8022	(1).....	(1).....	Ferruginous sandstone.....	12,130
8023	(1).....	(1).....do.....	14,000
8024	(1).....	(1).....do.....	12,480
11190	Shohola.....	Pike.....	Feldspathic sandstone.....	25,250
9812	Holmesburg.....	Philadelphia.....	Biotite gneiss.....	21,530
3243	McSpadden.....	Somerset.....	Sandstone.....	26,900
10345	Confluence.....do.....	Calcareous sandstone.....	24,790
5830	Prompton.....	Wayne.....	Feldspathic sandstone.....	26,340
5605	Blairsville Intersection.....	Westmoreland.....	Siliceous limestone.....	32,560
7428	York.....	York.....	Dolomitic marble.....	27,400

RHODE ISLAND.

8867	Westerly.....	Washington.....	Granite.....	11,740
8868do.....do.....do.....	20,300
8869do.....do.....do.....	20,750

SOUTH CAROLINA.

8389	Williamstown.....	Anderson.....	Granite.....	12,990
5568	Rion.....	Fairfield.....do.....	29,180
5586ado.....do.....do.....	25,790
5586bdo.....do.....do.....	19,240
5586cdo.....do.....do.....	33,880
10531do.....do.....	Biotite granite.....	25,540

TENNESSEE.

5597	Quarry.....	Carter.....	Limestone:.....	22,750
5502	Straw Plains.....	Jefferson.....do.....	21,730
5504do.....do.....do.....	28,340
5503do.....do.....	Dolomite.....	38,070
6533	Knoxville.....	Knox.....	Marble.....	17,970

VERMONT.

5543	East Wallingford.....	Rutland.....	Altered diabase.....	16,800
8853	Barre.....	Washington.....	Granite.....	19,560

¹ Exact locality not known.

TABLE II.—*Results of compression tests of rock complete to Jan. 1, 1917—Continued.*

VIRGINIA.

Serial No.	Locality.	County.	Name.	Crushing strength, pounds per square inch.
8804	Albert.....	Bedford.....	Granite gneiss.....	13,820
10344	Lynchburg.....	Campbell.....	Quartzite.....	25,885
6796	(1).	Dinwiddie.....	Granite.....	13,150
4900A	Broad Run.....	Fauquier.....	Quartz.....	28,400
4900Bdo.....do.....	Epidote.....	28,000
5923	Strathmore.....	Fluvanna.....	Chlorite epidote schist.....	13,210
5678	Egglesston (near).....	Giles.....	Dolomite.....	45,690
5924	Boscobel.....	Goochland.....	Granite gneiss.....	13,550
6615	Korah Station.....	Henrico.....	Biotite granite.....	20,300
5925	Greenway.....	Nelson.....	Feldspathic quartzite.....	16,500
5492	Nokesville.....	Prince William.....	Ferruginous sandstone.....	17,780
5920	Greenlee.....	Rockbridge.....	Dolomitic marble.....	36,900
5382	Bluff Water Station.....	Rockingham.....	Limestone.....	21,450
5385do.....do.....do.....	40,850
5375	St. Paul.....	Russell.....do.....	17,600
7217	Burkes Garden.....	Tazewell.....	Dolomitic sandstone.....	21,500

WEST VIRGINIA.

5365	Berkeley.....	Berkeley.....	Limestone.....	23,350
5917	Remick.....	Greenbrier.....	Crystalline limestone.....	21,300
5918	Frazier.....do.....	Limestone.....	17,450
5919	Snow Flace.....do.....do.....	13,550
7475	Green Spring, east of.....	Hampshire.....	Siliceous limestone.....	34,400
7476do.....do.....	Quartzite.....	15,050
6109	Spring Hill.....	Kanawha.....	Sandstone.....	12,400
9132	Fairmont.....	Marion.....do.....	5,420
9133do.....do.....do.....	5,720
9134do.....do.....do.....	6,080
5610	Sturgisson.....	Monongalia.....	Siliceous limestone.....	22,440
5612do.....do.....	Limestone.....	17,910
5613do.....do.....	Argillaceous limestone.....	14,300
5614do.....do.....	Calcareous sandstone.....	29,840
5615do.....do.....	Pure limestone.....	19,650
5616do.....do.....	Argillaceous limestone.....	24,850
8447	Parkersburg.....	Wood.....	Feldspathic sandstone.....	11,910

WISCONSIN.

5523	Peebles.....	Fond du Lac.....	Dolomite.....	32,600
3448	Amberg.....	Marinette.....	Biotite granite.....	20,000
11129	Wauwatosa.....	Milwaukee.....	Argillaceous dolomite.....	45,310
8656	Lannon.....	Waukesha.....	Dolomite.....	23,020

¹ Exact locality not known.TABLE III.—*Geographical distribution of rock samples tested to Jan. 1, 1917.*

Alabama.....	31	Kansas.....	13	New Jersey.....	75	Utah.....	13
Arizona.....	3	Kentucky.....	46	New Mexico.....	1	Vermont.....	35
Arkansas.....	17	Louisiana.....	7	New York.....	148	Virginia.....	424
California.....	101	Maine.....	86	North Carolina.....	149	Washington.....	213
Colorado.....	28	Maryland.....	121	Ohio.....	165	West Virginia.....	180
Connecticut.....	52	Massachusetts.....	192	Oklahoma.....	50	Wisconsin.....	149
Delaware.....	30	Michigan.....	95	Oregon.....	14	Wyoming.....	3
Florida.....	13	Minnesota.....	17	Pennsylvania.....	610	Canada.....	52
Georgia.....	256	Mississippi.....	13	Rhode Island.....	41	Porto Rico.....	12
Idaho.....	10	Missouri.....	39	South Carolina.....	30	Cuba.....	4
Illinois.....	128	Montana.....	4	South Dakota.....	15		
Indiana.....	179	Nebraska.....	12	Tennessee.....	77	Total.....	4,066
Iowa.....	23	New Hampshire.....	27	Texas.....	63		

By comparing the results of tests on a sample of rock with the limits as shown in the following table, a general idea of the types of road construction for which it is best suited may be obtained.

TABLE IV.—*General limiting test values for broken stone.*

Type of construction.	Traffic. ¹	Limiting values.		
		French coefficient of wear.	Toughness.	Hardness.
Water-bound macadam, plain or with dust palliative treatment.	{ Light..... Moderate..... Heavy.....	5 to 8 9 to 15 16 or over.	5 to 9 10 to 18 19 or over.	10 to 17 14 or over. 17 or over. (2)
Macadam with bituminous carpet.....	Light to moderate.....	5 or over.	5 or over.	
Bituminous macadam with seal coat.....	Moderate to heavy.....	7 or over.	10 or over.	
Bituminous concrete.....	{ Light to moderate..... (Moderate to heavy..... Any.....	7 or over. 10 or over. 7 or over.	7 or over. 13 or over. 6 or over.	(2) ----- (2)
Binder course for sheet asphalt or Topeka type.				
Portland cement concrete.....	Moderate to heavy.....	(3)	8 or over.	16 or over.
Stone paving block ⁴ .	Any.....	(3)	9 or over.	16 or over.
Broken stone foundations.....	do.....	3 or over.	3 or over.	8 or over.
Cement concrete foundations.....				

¹ Light traffic is assumed as less than 100 vehicles per day, moderate traffic between 100 and 250 vehicles, and heavy traffic over 250 vehicles per day.

² Numerous tests have shown that limits for hardness are unnecessary if the material possesses the required French coefficient of wear and toughness.

³ Limits for French coefficient of wear are not at present considered necessary for this type of construction.

⁴ Crushing strength, 20,000 pounds or over per square inch is sometimes required.

Cementing values should show over 25 in all cases if material is to be used in water-bound macadam construction.

In general, granites, gneisses, schists, sandstones, and quartzites should not be used in the wearing course of water-bound macadam roads. Shales and slates never should be used in this connection; therefore cementing value tests have been discontinued on these materials.

For further details and explanation of results in this table and also for tests on all materials to January 1, 1916, see U. S. Department of Agriculture Bulletin No. 370.

ADDITIONAL COPIES

OF THIS PUBLICATION MAY BE PROCURED FROM

THE SUPERINTENDENT OF DOCUMENTS

GOVERNMENT PRINTING OFFICE

WASHINGTON, D. C.

AT

5 CENTS PER COPY

